

Pair Interaction Potentials of Colloids by Extrapolation of Confocal Microscopy Measurements of Collective Suspension Structure

Christopher R. Iacovella,¹ Reginald E. Rogers,¹ Sharon C. Glotzer,^{1,2} and Michael J. Solomon¹

¹⁾*Department of Chemical Engineering*

University of Michigan, Ann Arbor, Michigan 48109-2136

²⁾*Department of Materials Science and Engineering*

University of Michigan, Ann Arbor, Michigan 48109-2136

(Dated: 28 October 2010)

A method for measuring the pair interaction potential between colloidal particles by extrapolation measurement of collective structure to infinite dilution is presented and explored using simulation and experiment. The method is particularly well suited to systems in which the colloid is fluorescent and refractive index matched with the solvent. The method involves characterizing the potential of mean force between colloidal particles in suspension by measurement of the radial distribution function using 3D direct visualization. The potentials of mean force are extrapolated to infinite dilution to yield an estimate of the pair interaction potential, $U(r)$. We use Monte Carlo (MC) simulation to test and establish our methodology as well as to explore the effects of polydispersity on the accuracy. We use poly-12-hydroxystearic acid-stabilized poly(methyl methacrylate) (PHSA-PMMA) particles dispersed in the solvent dioctyl phthalate (DOP) to test the method and assess its accuracy for three different repulsive systems for which the range has been manipulated by addition of electrolyte.

I. INTRODUCTION

Colloidal systems may undergo crystallization because of the effects of packing and excluded volume¹, repulsive or attractive charge^{2,3}, and/or weak attractions caused by additives such as non-absorbing polymer⁴. Moreover, the phase behavior can often be dramatically changed by making only small modifications to the particle-particle interactions^{3,5,6}. Knowledge of the interaction between colloidal particles and the ability to tune these interactions is important for designing and assembling target materials. Target materials, such as self-assembled arrays of colloids, have potential applications as periodic dielectrics⁷, photonic band gap materials⁸, and chemical and biological sensors⁹. The pair interaction potential, $U(r)$, which characterizes the potential energy change that results as two isolated particles are brought from an infinite to a finite separation, is a common parameterization of the interaction between colloids. The ability to parameterize particle interactions into pair potentials allows simulation and theory to be readily incorporated into the experimental design process. Simulation and theory have been shown to be valuable tools for predicting and explaining structures and trends in colloidal systems. For example, simulation and theory have been used to calculate the crystal-nucleation rate of hard-sphere colloids¹⁰, phase behavior of attractive⁵ and repulsive⁶ colloids, and the stability of binary ionic colloidal crystals³. Thus, characterization of $U(r)$ for colloidal particles is an important step in the process of predictably assembling target phases.

Common techniques for measuring the interaction potential of colloidal particles include colloid probe atomic force microscopy (AFM)¹¹, surface force apparatus¹², total internal reflection microscopy (TIRM)¹³, and optical tweezers¹⁴. Each of these techniques allows for the direct measurement of the pair interaction potential between isolated particles and surfaces. While these techniques provide valuable information about colloidal interactions their applications to the problems of colloidal assembly are limited because, with the exception of optical tweezers^{15,16}, they do not characterize particle-particle interactions directly, which is often more relevant to the study of self-assembly of bulk colloids. Additionally, TIRM and optical tweezers are not generally applicable to refractive index matched colloidal systems since these technique require refractive index contrast for optimal performance. Often, colloidal systems that are useful for self-assembly are approximately refractive index matched, which minimizes strong attractive interactions due to van der Waals forces that tend to

trigger gelation and irreversible aggregation¹⁷.

For colloids that are refractive-index matched, fluorescent and approximately $1\mu\text{m}$ in size, fluorescence or confocal microscopy methods can be used to characterize structure and order in such suspensions¹⁸. The ability to directly quantify the structure enables the use of statistical physics methods to characterize the interaction potential. This technique involves calculating the radial distribution function, $g(r)$, and extracting the potential of mean force, $W(r)$, using the following relationship¹⁹,

$$W(r)/k_bT = -\ln[g(r)] \quad (1)$$

where k_b is the Boltzmann constant and T is the temperature. $W(r)$ is a volume fraction (i.e. density) dependent measure of interaction; to determine the pair potential $U(r)$, and not simply a potential of mean force, an extrapolation to the limit of infinite dilution is required, as we will discuss in this work. These methods are complementary to the previously discussed ones because they can often be performed on the exact system that will be used in self-assembly (i.e. a bulk solution of colloids). This basic treatment appears in various implementations in the literature. Several groups have examined bulk solutions of colloids, capturing particle positions using video microscopy¹⁹ and confocal laser scanning microscopy^{20,21}. In general, these groups calculate $g(r)$ from the microscopy data of a suspension at a particular “dilute” concentration and apply equation 1 to arrive at an “effective” pair potential at a finite volume fraction^{19–21}. That is, the method of these papers assumes that at dilute concentrations the potential of mean force approximates the pair potential. Hsu et al.²² approached the problem by using bright-field microscopy. Using a quasi-2D methodology, they captured many statistically independent images of particles interacting with one another, and then computed the 2D radial distribution function to extract the pair potential. To corroborate their results, they employed Monte Carlo (MC) simulations to calculate $g(r)$. Wu and Bevan²³ took advantage of TIRM and video microscopy to capture the interaction forces between particles. In this case, colloidal pair interactions were assessed by separating out the additional contribution of the surface that is present in TIRM studies. Finally, Lu et al.²⁴, to support studies of gelation, parameterized short-range attractive potentials of micron-sized colloids by comparing measurements of the second virial coefficient and the cluster mass distributions to the results of MC and molecular dynamics simulations. Overall, this class of techniques has been shown to be successful in many applications, pro-

viding results that are both consistent with theoretical behavior and simulation results. A drawback of this basic methodology is that there is no clear definition of what is “dilute” and, as we discuss in detail in this paper, if we do not sample in the correct regime this method can produce results that appear qualitatively correct but are quantitatively wrong. Moreover, this paper shows that the quantitative effect of the extrapolation methodology we propose should not be underestimated and that measurements of collective structure converted to effective potentials at a small but still finite volume fraction, i.e. assuming $W(r) = U(r)$ at low volume fraction, are prone to significant systematic error.

In this work, we outline a general procedure for the determination of the pair interaction potential, $U(r)$. In this procedure we use linear regression to extrapolate the potentials of mean force, $W(r)$, at finite concentrations to infinite dilution. We use both simulation and experiment to assess the validity of this method and provide guidelines for its use. In section II A we detail our method for determining the pair potential, providing a rational basis from statistical mechanics. In section II B we introduce our simulation model and method, and in section II C we introduce our experimental method. In section III A we use simulation to determine the dilute limit, i.e. the regime where the two body forces are dominant and $W(r)$ scales linearly with volume fraction. In section III B we use simulation to test the accuracy of the extrapolation method. In section III C we explore the role of polydispersity as it affects the potential derivation. In section IV we apply the guidelines from section II to an experimental system of fluorescently labeled poly-methyl methacrylate (PMMA) particles stabilized by poly-12-hydroxystearic acid (PHSA) and compare to the theoretical screened Coulombic potential. In Section V we provide concluding remarks.

II. METHODOLOGIES

A. Method for determining $U(r)$ from the potentials of mean force

Following Chandler²⁵, we can develop a rational basis for our method from statistical mechanics. Starting with:

$$g(r) = e^{-\beta W(r)} \quad (2)$$

we have a relationship between the radial distribution function, $g(r)$, and the potential of mean force, $W(r)$. $W(r)$ represents the reversible work for the process of moving two

particles from infinite separation to a finite separation of r . $W(r)$ can be separated into two parts:

$$W(r) = U(r) + \Delta W(r) \quad (3)$$

where $U(r)$, the pair potential, is the reversible work to move two isolated particles to a separation of r at infinite dilution, and $\Delta W(r)$ is the contribution to $W(r)$ due to the density of the system (i.e. interactions with surrounding particles in the system, not many body forces. This can additionally be thought of as moving through a potential landscape resulting from the presence of other particles). Combining equations 2 and 3 and taking the natural log, we arrive at:

$$\frac{-\ln g(r)}{\beta} = U(r) + \Delta W(r) \quad (4)$$

In the limit of infinite dilution (i.e. when the volume fraction, ϕ , goes to zero) we have $\lim_{\phi \rightarrow 0} \Delta W(r) = 0$, and thus:

$$\lim_{\phi \rightarrow 0} \frac{-\ln g(r)}{\beta} = \lim_{\phi \rightarrow 0} W(r) = U(r) \quad (5)$$

Equation 5 is the basis for our method for determining $U(r)$. To avoid confusion, we will now refer to the potential of mean force as $W(r, \phi)$ and the radial distribution function as $g(r, \phi)$, to highlight the volume fraction dependence. The general procedure to calculate $U(r)$ is as follows:

1. Calculate $g(r, \phi)$ at a series of finite, dilute values of ϕ
2. Calculate $W(r, \phi)$ from $g(r, \phi)$, using equation 1, for each value of ϕ
3. For each value of r , perform a linear regression of $W(r, \phi)$ vs. ϕ
4. For each value of r , evaluate the linear regression at $\phi = 0$ to construct an estimate of $U(r)$

We should note that unlike other methods in the literature, this method does not rely on a single $g(r, \phi)$ but rather on the behavior of a collection of $g(r, \phi)$ data over a range of ϕ . In section II we will explore the benefits of using a collection of $g(r, \phi)$ data and will provide guidelines for the use of this method. It is important to note that this methodology only

applies to systems where many body forces are negligible. It has been shown that when the electrostatic screening length is less than the interparticle separation, the assumption of pairwise additivity is well suited to predict the forces between colloids²⁶; the experimental systems we study in this paper fit this criteria. It is additionally important to note that the charge of the colloids may be a function of ϕ , thus making the application of $U(r)$ to higher density systems problematic²⁷; however, this is an issue with all methods that determine the interaction at low ϕ and will not be specifically addressed in this article.

B. Simulation Method and Model

To study the various aspects of colloidal pair interactions, we performed NVT Monte Carlo (MC) simulations that employ the Metropolis sampling algorithm²⁸. Simulation is powerful in this application since we explicitly know the “true” interaction potential (i.e. it is programmed into the simulation code), have exact control over polydispersity and volume fraction, and have no artifacts associated with identification of the particle centroid. Thus we can assess the accuracy of the potential derivation method under well controlled, ideal conditions. We conducted simulations of spherical particles that interact via screened Coulombic interactions, modeled using the Yukawa potential⁶, given as:

$$\frac{U(r)}{k_bT} = \epsilon \frac{\exp[-\kappa\sigma(r/\sigma - 1)]}{r/\sigma} \quad (6)$$

where κ is the inverse Debye length, σ is the particle diameter, and ϵ is the energy at contact (dimensionless, scaled by k_bT). In our simulations, particles were treated as hardcore and not allowed to overlap (i.e. $U(r)/k_bT = \infty$ when $r/\sigma < 1$); the potential was truncated at a distance r when $U(r)/k_bT \leq \epsilon/60$ ²⁸. In the limit of very large κ , the Yukawa potential becomes very short-ranged and essentially reduces to the hard sphere potential, only capturing excluded volume¹⁰. We used the hard sphere potential, given by equation 7, to investigate this limit.

$$\frac{U(r)}{k_bT} = \begin{cases} \infty, & r \leq \sigma \\ 0, & r > \sigma \end{cases} \quad (7)$$

To model polydispersity in particle size, particle diameters were set based on a prescribed Gaussian distribution where the average particle diameter is given as σ . Particle interactions

were modeled by Equations 6 and 7, however the radial separation, r , was adjusted based upon the deviation from the mean diameter. Specifically for a pair of particles i and j , with diameters σ_i and σ_j , respectively, and a center-to-center separation of r , the scaled radius, r_{scaled} , is given by:

$$r_{scaled} = r - 0.5(\sigma_i - \sigma) - 0.5(\sigma_j - \sigma) \quad (8)$$

Note that eqn 8 reduces to $r_{scaled} = r$ when $\sigma_i = \sigma_j = \sigma$. Thus, the Yukawa potential for a polydisperse set of particles is given as:

$$\frac{U_{ij}(r)}{k_b T} = \epsilon \frac{\exp[-\kappa \sigma ([r + \sigma - 0.5\sigma_i - 0.5\sigma_j]) / \sigma - 1]}{r / \sigma} \quad (9)$$

where again, σ is the mean particle diameter. This fixes the interaction range of the potential with respect to the surface of the particle. This assumption is reasonable since the Debye length ($1/\kappa$) is the dominant parameter in determining interaction range and is independent of particle diameter. Additionally, for simplicity, we make the assumption that the energy at contact is not a function of particle diameter, instead focusing primarily on the role excluded volume interactions play in polydispersity. Such an assumption appears reasonable; with a fixed ϵ value, a 5% increase or decrease in particle diameter only results in a $\sim 2.5\%$ change in the charge number, Z , and a 10% change only results in $\sim 5\%$ change in Z , as calculated using equation 10.

In all cases, we used system sizes of 1000 spherical particles in a periodic box and fixed the dimensionless temperature at a value of 1. For each system we started from a random, disordered configuration and allowed the system to run for approximately one million MC timesteps, collecting data every 1000 MC timesteps. System size effects should be minimal considering the low volume fractions studied and relatively short-ranged interaction; the box length was substantially larger than the range of interaction for all conditions studied (e.g. for $\phi = 0.1$ the box length, $l_{box} > 17\sigma$ and for $\phi = 0.001$, $l_{box} > 80\sigma$). Dimensionless temperature is defined as $T^* = k_b T / \epsilon$. The interaction potential programmed into the simulation code will be referred to as the “known” interaction potential.

C. Experimental Method

1. *Synthesis and Characterization of PHSA-stabilized PMMA Particles*

Non-aqueous solvents are often selected for colloidal assembly because they offer the possibility of matching the solvent and particle refractive index, thereby minimizing attractive van der Waals interactions that can interfere with assembly. A common choice for assembly includes mixtures of cyclohexyl bromide and decalin²⁹. An alternative choice, particularly useful for confocal microscopy, rheology and field-assisted assembly is dioctyl phthalate^{30,31}. Because of its high viscosity, this solvent is particularly compatible with the scan rate of confocal microscopy, and we use it to test our method for that reason.

Fluorescently-labeled poly(methyl methacrylate) particles stabilized by poly-12-hydroxysteric acid (PHSA) were synthesized using an adaptation of the methods of Antl et al.³², Campbell and Bartlett³³, and Pathmamanoharan et al.³⁴, as discussed by Solomon and Solomon³⁰. Particles were labeled using Nile red dye. Previous work has shown that PHSA-PMMA colloids in cyclohexyl bromide (CHB) and decalin are charged²⁹. Shereda *et al.* also reported particle charging for these particles in DOP³¹. Such colloidal systems have been modeled by the Yukawa pair potential (equation 6) where we explicitly define:

$$\epsilon = \frac{Z^2 \lambda_B}{\sigma_p k_B T (1 + \kappa \sigma_p / 2)^2} \quad (10)$$

where Z is the charge number, λ_B is the Bjerrum length (11 nm for the system studied here³⁵), and κ is the inverse Debye length³.

Parameters in equations 6 and 10, estimated by experiment, are reported in Table II C 1. κ^{-1} was estimated from conductivity measurements. Briefly, solutions of dioctyl phthalate (DOP; Sigma-Aldrich, used as received) containing 10 μ M and 2mM of tetrabutylammonium chloride (TBAC) salt were prepared and their conductivity measured with devices (Model 1154 Precision Conductivity Meter, Emcee Electronics, Venice, Florida or Model EW-01481-61, Cole-Parmer, USA) whose performance was verified by measurements with known standards. As per the method of reference²⁹, using Waldens rule³⁶⁻³⁸ (viscosity of DOP = 71 mPa s at 25C³⁹ and reference ion mobilities in water at 25C (as taken from reference²⁹ TBA⁺ ion mobility is 19.4 cm² S mol⁻¹ and Cl⁻ is 76.3 cm² S mol⁻¹), the ion concentration was determined and calculated using equation 11:

$$\kappa = \sqrt{8\pi\lambda_B\rho_i} \quad (11)$$

where ρ_i is the density of the cation or anion²⁹. The Debye length of salt-free DOP was not determined in this way because of the uncertain identification of the mobile ions in this solvent. Thus, in this case, a one-parameter fit to the extrapolated pair potential (as discussed in the results) was made and a value of 440 nm was obtained. This value is included in the table for completeness. This Debye length is qualitatively consistent with literature reports⁴⁰ of the very low conductivity ($\sim 2.3 \times 10^{-9}$ S/m) of dioctyl phthalate.

The charge number of the PHSA-stabilized PMMA particles was determined from measurements of their electrophoretic mobility (Zetasizer Nano Series, Malvern, United Kingdom). Particles were prepared as 1 vol percent solutions in pure DOP solvent (i.e. [TBAC] = 0), [TBAC] = 10 μ M, and [TBAC] = 2mM. Solutions were placed in a dip cell designed for non-aqueous solvents. A voltage of 50mV was applied to each sample and three independent samples were studied. Using the calculated Debye length and measured mobility, the zeta potential was determined by the method of O'Brien and White⁴¹. The charge number on the particles was determined from:

$$Z = \frac{q}{e} = \frac{4\pi\epsilon_0\epsilon_r(\sigma/2)\zeta(1 + \kappa\sigma/2)}{e} \quad (12)$$

where q is the particle charge, e is the charge on an electron, ϵ_0 is the permittivity in a vacuum, ϵ_r is the relative dielectric constant of DOP ($\sim 5.10^{42}$), and ζ is the zeta potential³⁵.

The distribution of particle diameters, determined from scanning electron microscopy (SEM) analysis of 250 particles, is plotted in Figure 1. From the best fit of the normal distribution, we determined the mean diameter to be $951\text{nm} \pm 38\text{nm}$. Because PMMA colloids may swell in organic solvents⁴³, we compared the SEM diameter to direct measurements of the colloid size in solution. To perform the comparison, we prepared a sample at a very high TBAC salt concentration of 50mM to induce aggregation of the particles in the solvent. A CLSM image volume was acquired and the separation between particle pairs was computed by image processing per the method described subsequently in section II C 3. We found the particles swell approximately 5% to 1001 ± 30 nm. This small change in diameter does not have a major effect on our measurements or $U(r)$. For consistency, we will report our findings based on the particle diameter measured by the CLSM method, since our experiments

were done in DOP solvent.

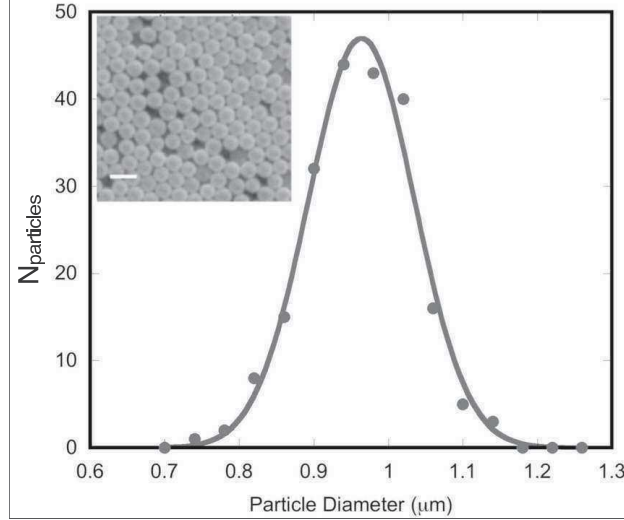


FIG. 1. Distribution of PHSA-PMMA particles diameters with fitted Gaussian curve shown as solid line; particles have a diameter of $951 \pm 38\text{nm}$. Inset is an SEM image of PHSA-stabilized PMMA particles used to generate the distribution; scale bar represents $2\mu\text{m}$.

DOP containing	κ^{-1} (nm)	ζ (mv)	Z_{CLSM}	ϵ_{CLSM}	$\kappa\sigma_{CLSM}$
No TBAC	440	-28	-100	27	2.2
10 μ M TBAC	250	-30	-160	31	4.0
2 mM TBAC	49	-32	-630	35	20

TABLE I. Electrokinetic measurements for the three experimental systems studied.

2. Sample preparation and image volume collection

In this work, we explored three different systems where the solvent and particles are approximately refractive index (RI) matched. The PMMA-PHSA particles ($\text{RI} = 1.489$) were dispersed in DOP ($\text{RI} = 1.485$) containing no salt, $10\mu\text{M}$ TBAC salt or 2mM TBAC salt. Samples were prepared at nominal volume fractions of $\phi = [0.005, 0.01, 0.015, 0.02, 0.03, 0.04, 0.05]$; however, precise estimation of the volume fraction was made from the results of quantitative image processing discussed in section II C 3. The samples were initially

mixed and then allowed to equilibrate for 24 hours. Samples were then gently remixed and subsequently transferred to glass specimen vials (outer diameter, O.D. = 12mm) that were adhered to a microscope cover slip using ultraviolet bonding glue (Dymax Corporation, United States). The cover slip was attached to a 35mm O.D. glass ring made from Pyrex standard wall tubing. To assess the stability of this colloidal system, samples prepared at $\phi = 0.005$ in the DOP solvent were monitored for 24 hours for signs of phase instability. No aggregation or phase instability was observed.

Sample imaging was performed on a Leica TCS SP2 confocal microscope (Leica Microsystems, Wetzlar, Germany). A 100x oil immersion objective with numerical aperture 1.4 was used. The particles were dyed with Nile red (Sigma-Aldrich, United States) and were excited with a green neon (GreNe) laser beam ($\lambda_0 = 543\text{nm}$). Emission from 550nm to 650nm was collected. To avoid possible effects of sample boundaries on particle configurations, all points in the image volumes were located at least $20\mu\text{m}$ from any boundary of the specimen vial. Stacks of 247 images with a resolution of 512×512 pixels were obtained and processed to extract particle centroids, as described in the next section. Images were acquired with a spatial resolution of $69.2 \times 69.2 \text{ nm/pixel}$ in the objective plane and an axial separation of 81.4 nm . Thus, the size of the image volume was $35 \times 35 \times 20 \mu\text{m}^3$.

3. Image Processing

To identify particle locations, we used image processing algorithms based on the work of Crocker and Grier⁴⁴ expanded to 3D systems⁴⁵ as discussed in Dibble et al.⁴⁶. First, a Gaussian filter was applied to the 3D image volume. Second, particle centers were identified using a local brightness maximum criterion. That is, a voxel was identified as a candidate centroid if it was the brightest within a local cubic region of half-width w . For our systems and imaging conditions, $w = 7$, which corresponded to approximately 485 nm . Finally, using the moments of the local intensity distribution, particle positions were refined to subpixel accuracy⁴⁷. For our setup, the accuracy was calculated to be $\pm 35 \text{ nm}$ in the $x - y$ plane and $\pm 45 \text{ nm}$ in the z direction in reference⁴⁶. $g(r, \phi)$ was calculated using the centroid locations. We assessed the accuracy of the image processing algorithm by examining composite images for which centroid locations were overlaid on the fluorescence images; the algorithm was found to identify nearly all of the particle centroids. We also validated the centroid

calculation for particles at close contact, finding no evidence of erroneous behavior, as has been observed for other systems^{48,49}. For our fluorescently labeled system, CLSM provided a strong contrast between particle and solvent, and does not produce an Airy pattern; thus we meet both conditions shown to be essential for accurate centroid determination outlined in reference⁴⁸.

III. SIMULATION RESULTS

A. Determining the Dilute Regime

The general method for calculating the pair potential involves linearly regressing $W(r, \phi)$ at finite values of ϕ , and evaluating the regression at $\phi = 0$. In order for this to be valid, we must be in a range where $W(r, \phi)$ scales linearly with ϕ (i.e. the regime where only 2-body forces are dominant and there are no strong volume fraction effects). Unfortunately, there is no general rule for what value of ϕ constitutes this dilute regime; the crossover between “dilute” and “concentrated” will be a function of the strength and relative range of the interaction. To determine the crossover, ϕ_{max} , we performed a series of simulations using the hard-sphere and Yukawa potentials over a range of ϕ . Specifically for the Yukawa potential, we performed simulations with $\epsilon = 3$ and $\kappa\sigma = (5.0, 3.0, 1.5, 1.0, 0.5, 0.25)$, $\epsilon = 50$ and $\kappa\sigma = (5.0, 3.0, 1.5, 1.0)$, and $\epsilon = 100$ with $\kappa\sigma = (5.0, 3.0, 1.5, 1.0)$ at a variety of values of ϕ . This allows us to explore the dependence of ϕ_{max} on both interaction range and interaction strength.

To determine ϕ_{max} , the maximum volume fraction for which $W(r, \phi)$ scales linearly with ϕ , we performed the following procedure. For each value of r/σ , we plotted $-\ln[g(r, \phi)]$ (i.e. $W(r, \phi)$) as a function of ϕ ; we included the pair potential as the value that occurs at $\phi = 0$. We then determined, by eye, the approximate crossover between linear and non-linear behavior. We then performed a linear regression on the subset of the data that appeared linear and fine-tuned our results. We looked at both the residual of the fitting of the data and compared between the known (i.e. the potential programmed into the simulation) and regressed value at $\phi = 0$ to determine the appropriate value of ϕ_{max} . Figure 2A plots an example of the crossover between “dilute” and “concentrated” regimes showing a region with distinct linear behavior; the extrapolation is also plotted showing near perfectly agreement

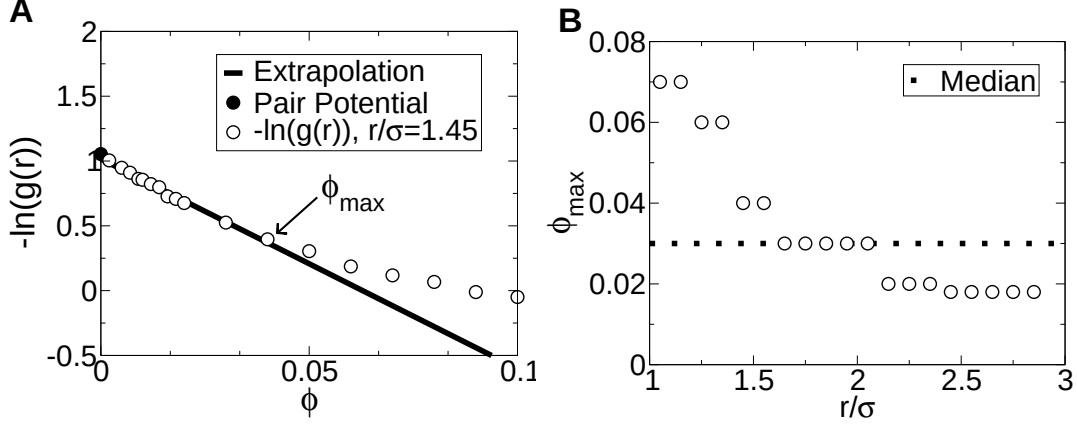


FIG. 2. For a Yukawa system with $\epsilon = 3$, $\kappa\sigma = 1.5$, (A) determination of the dilute regime where is the crossover, and (B) vs. where the median value appears as the dotted line.

with the known interaction potential value. This procedure was applied to all values of r/σ , creating a data set for each potential that is of the form of ϕ_{max} vs. r/σ ; an example data set is plotted in Figure 2B. We should note that in Figure 2B it is clear that ϕ_{max} decreases as we increase r/σ and it is not simply a single value for a given pair interaction. The dependence of ϕ_{max} on r/σ for a fixed ϵ and $\kappa\sigma$ can be understood by thinking in terms of the “effective” diameter of the particle. That is, if we were to increase the diameter of our particle, we would need to increase our system volume to maintain the same ϕ . The quantity r/σ can be considered to be proportional to the “effective” diameter of the particles, thus, as we increase r/σ we need to also increase our system volume to maintain the same effective ϕ , as we see in Figure 2B (i.e. increasing system volume is analogous to a decrease ϕ since ϕ is calculated using the excluded volume diameter, σ , not an effective diameter). As such, we calculated the median value of ϕ_{max} , as this should be representative of the data and not biased by the large values of ϕ_{max} at small r/σ .

The median values are summarized in Figure 3. The data sets were grouped by ϵ and fitted with a power law to guide the eye. We see that as $\kappa\sigma$ decreases (i.e. our potential becomes longer ranged with respect to particle diameter), $\phi_{max,median}$ decreases. Additionally, as ϵ increases, we find that $\phi_{max,median}$ also decreases, however not as rapidly as the trends with $\kappa\sigma$. We also see that for the hard-sphere system, $\phi_{max,median} = 0.2$, and this can be taken as an upper limit for all repulsive systems; $\phi_{max,median}$ for hard-spheres was calculated using the same procedure as the Yukawa systems and corresponds to a state where $\kappa = \infty$, thus

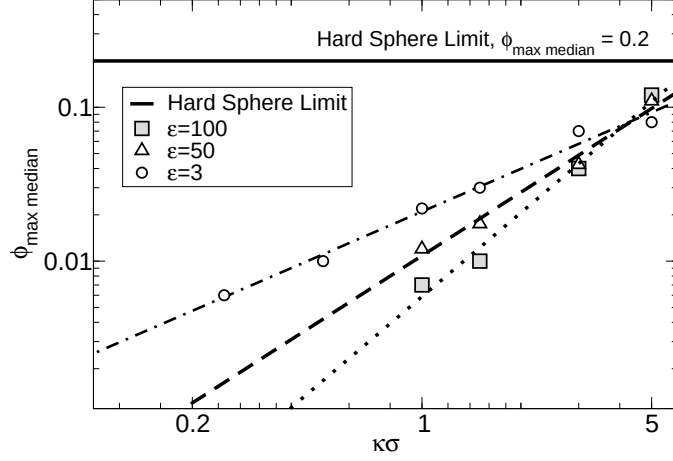


FIG. 3. The median value of ϕ_{max} vs. $\kappa\sigma$ showing the approximate crossover between concentrated and dilute regimes. Data for each ϵ value are fitted with a power law best fit to guide the eye.

it is plotted as a bounding line. It is clear that as the range of the potential increases, we must sample at increasingly lower volume fractions.

Figure 3 can be used as a rough guideline to determine the appropriate regime to collect data for the calculation of $U(r)$. While this plot depends on *a priori* knowledge of $\kappa\sigma$ and ϵ – the values we ultimately wish to calculate – we only need a rough estimate of the screening length to use this plot. As previously stated, the median value of $\phi_{max, median}$ depends predominantly on $\kappa\sigma$ which can be roughly estimated with minimal effort by measuring at a low value $g(r, \phi)$ (e.g. $\phi = 0.01$ is satisfactory for the systems presented in Figure 3). In practice, the values of ϕ_{max} should be assessed for each system studied using the methodology previously described; Figure 3 should be used as a rough guide to approximate where this regime occurs, to avoid collecting unnecessary data.

B. Accuracy of the Extrapolated Potential

We applied the extrapolation method to our Monte Carlo simulations and found excellent agreement between the extrapolated potentials and the pair potentials programmed into the simulation; note in these cases we treated the system as monodisperse with respect to particle diameter. In Figure 4 we plotted the known potential and the extrapolated potential for an example system with $\epsilon=3$ and $\kappa\sigma=1.5$. We extrapolated $W(r, \phi)$ for 11 values of ϕ ranging from 0.002 to 0.03, using the median value of $\phi_{max, median} = 0.03$ as the maximum cutoff for

the regression; we did not take into account the r/σ dependence of ϕ_{max} for this test. We see that the extrapolated potential is virtually identical to the known potential, as shown in Figure 4. To parameterize the accuracy of the extrapolated potential, we calculated the magnitude of the difference between the test and known potentials, normalized by the magnitude of the two potentials (represented as vectors),

$$M = \frac{\sum_i^{max} |U_{test}(r_i) - U_{known}(r_i)|}{\sum_i^{test} |U_{test}(r_i)| + \sum_i^{max} |U_{known}(r_i)|} \quad (13)$$

where max is the total number of discrete points considered; in this measure an ideal match has $M = 0$ and the maximum difference has $M = 1$. We used M rather than the relative error since M is always normalized between 0 and 1 for all potentials and number of data-points considered. Additionally, by its construction, M is weighted with respect to the total magnitude of both vectors we compare, thus we avoid any erroneously large errors associated with the difference between relatively small values (e.g. $U(r) = 0.05$ and $U(r) = 0.01$ are nearly indiscernible on the energy scale we consider here, however their relative error is 4, whereas the difference between $U(r) = 10$ and $U(r) = 6$ would be clearly evident, yet the relative error is much less with a value of 0.67). The difference between the extrapolated potential and known pair potential in Figure 4 was calculated to be $M=0.023$.

The advantage of using the regression method over a single “dilute” concentration is also highlighted in Figure 4. We plotted $W(r, \phi)$ for two different volume fractions, $\phi = 0.05$ and 0.005 . For a value of $\phi = 0.05$, a relatively low-density system, we capture the gross behavior, however the actual values deviate substantially from the known potential. $W(r, 0.05)$ significantly undershoots the known potential and any values of ϵ and κ extracted from this plot would be misleading; for $W(r, 0.05)$, $M = 0.497$. We also plotted $W(r, \phi)$ for $\phi = 0.005$, a very low density sample, and find this to be a reasonable approximation to the known potential with $M = 0.063$.

Without prior knowledge of the known potential – besides the notion it should be repulsive – it would be difficult to assess if $W(r, 0.05)$ or $W(r, 0.005)$ are good approximations of the pair potential. In order to assess whether the potential of mean force is reasonable, we would need to follow a procedure similar to that outlined in reference¹⁹; we would need to collect additional data at lower ϕ values and see if $g(r, \phi)$, or alternatively $W(r, \phi)$, changed substantially as ϕ was decreased¹⁹. In effect, we would need to collect, analyze, and calculate

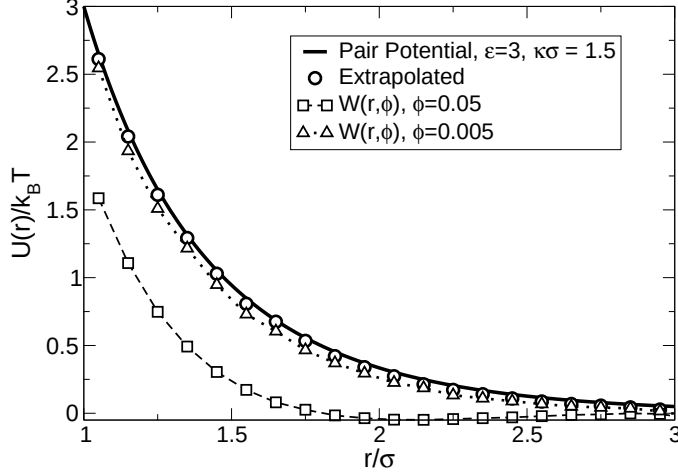


FIG. 4. For a Yukawa system with $\epsilon = 3$ and $\kappa\sigma = 1.5$, the pair potential and extrapolated potentials are plotted showing excellent agreement. The extrapolated potential was calculated from 11 values of ϕ ranging from 0.002-0.03. $W(r, \phi)$ is also plotted for $\phi = 0.05$ and 0.005. $M = 0.023$ for the extrapolated potential, $M = 0.497$ for $W(r, 0.05)$, and $M = 0.063$ for $W(r, 0.005)$

additional data that would not necessarily be directly used to calculate the approximation of the pair potential. Therein lies a substantial benefit of the extrapolation method. In addition to calculating a more accurate approximation of the pair potential, we use nearly all data collected to calculate it, thereby increasing our overall confidence in the result; this procedure also provides a built-in “check” regarding the appropriateness of the derived potential in terms of its dependence on ϕ (i.e. if $W(r, \phi)$ does not scale linearly with ϕ , we are not dilute enough).

In Figure 5 we plotted the extrapolated potentials calculated for $\epsilon = 3$, and $\kappa\sigma = (5.0, 3.0, 0.5, 0.25)$ to explore the behavior of this method as a function of screening length. As in Figure 4, we ignored the r/σ dependence of ϕ_{max} and used only the median value. The extrapolation method worked well in all cases. The average magnitude of the difference between the known pair potential (i.e. the potential coded into the simulation) and extrapolated potential for $\epsilon = 3$ and $\kappa\sigma = (5.0, 3.0, 0.5, 0.25)$ is $M = (0.028, 0.021, 0.046, 0.087)$, respectively. As the range of the potential increases (i.e $\kappa\sigma$ becomes smaller), the method slightly underestimated the known value of the pair potential at larger r/σ values; this was most evident for $\kappa\sigma = 0.25$. As the range of the potential increases, the median of ϕ_{max} , or any single value, is less representative of the data on a whole, and a more careful treatment

of the regression should be applied (i.e. ϕ_{max} should be determined for each value of r/σ). However, the deviations are still well within the expected experimental error.

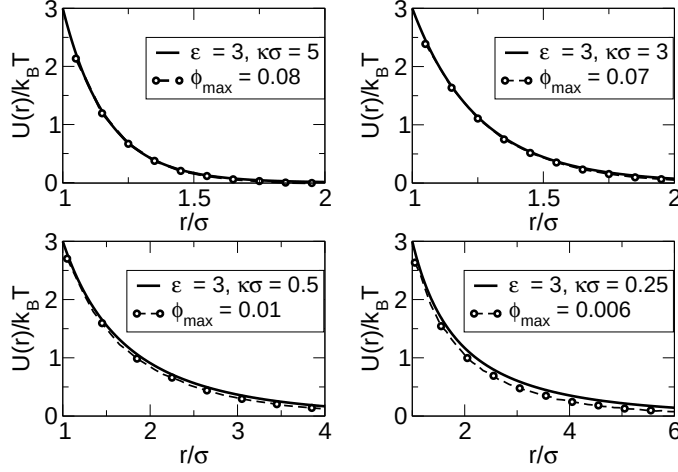


FIG. 5. Comparison between the known and extrapolated pair potentials. In all cases, the known potential is shown as a solid black line, and the extrapolated potential is shown as circles. In all cases, the extrapolated potential matches the known potential showing only minor deviations as the range of the potential is increased (i.e. $\kappa\sigma$ decreases).

In Figure 6 we explored the impact of ϵ on the extrapolation method, plotting the results for system where $\epsilon = 50$ and $\kappa\sigma = (3.0, 1.0)$ and $\epsilon = 100$ and $\kappa\sigma = (3.0, 1.0)$. In all cases, the extrapolation method matched the known potential well. The average magnitude of the difference between the known and extrapolated potentials for $\epsilon = 50$ and $\kappa\sigma = (3.0, 1.0)$ is $M = (0.038, 0.087)$, respectively and for $\epsilon = 100$ and $\kappa\sigma = (3.0, 1.0)$ $M = (0.022, 0.024)$, respectively. However, we see that the extrapolation method does not resolve values of $U(r)/k_B T$ greater than ~ 10 . This is not a failing of the method, but rather a consequence of the nature of the strong interactions in these cases. That is, as the strength of the potential is increased, the likelihood of two particles coming into very close contact is lowered.

C. Effect of Polydispersity

In sections III A and III B we treated our model colloidal particles as ideal and thus ignored polydispersity in particle diameter. In practice, experimental systems will contain

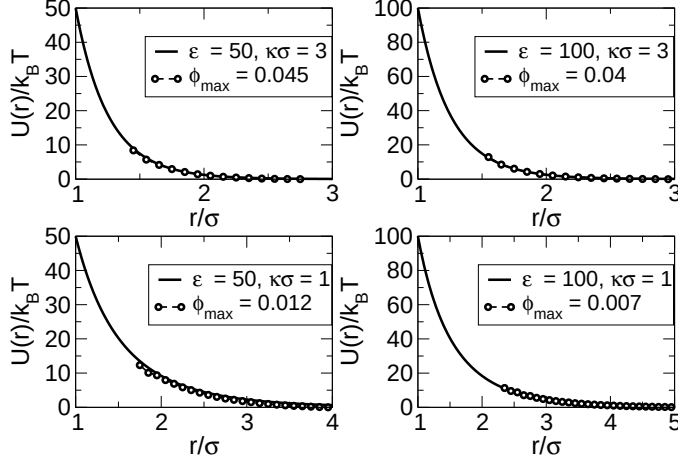


FIG. 6. Comparison between the known and extrapolated pair potentials. In all cases, the known potential is shown as a solid black line, and the extrapolated potential is shown as circles. The extrapolated potential matches the known potential well in all cases, however, we can only resolve the potential on the order of $\sim 10 k_B T$.

particles with a range of diameters, often distributed with Gaussian behavior, as we observed in Figure 1. Polydispersity is defined as, $P = (100 \%) (\text{standard deviation of particle diameter}) / (\text{average particle diameter})$. The experimental systems we explored in this work (see section II C) have polydispersity levels of $P \sim 4\%$ and this level is not atypical of colloidal systems for self-assembly. Polydispersity has been shown to have a large effect on phase behavior, for instance creating a phase separated crystal under high density when $P > 8\%$ ⁵⁰. However, since we are in the dilute regime, the effects of polydispersity may be muted. In our simulations, we initialized our particle diameters based on a Gaussian distribution that satisfied the given level of polydispersity we wish to study; our methodology was previously described in section II B.

We simulated three Yukawa systems with $\epsilon = 3$ and $\kappa\sigma = 5$, $\epsilon = 3$ and $\kappa\sigma = 10$, and $\epsilon = 43$ and $\kappa\sigma = 20$, each for $P = (0 \%, 5 \%, 10 \%)$; the extrapolations are shown in Figure 7. For $\epsilon = 3$ and $\kappa\sigma = 5$, polydispersity has a minimal effect on the extrapolation if we consider the extrapolated $U(r)$ for $r/\sigma \geq 1$, i.e we do not consider r/σ values that are less than the separation between two average diameter particles. Specifically, for $P = (0, 5, 10)\%$ we find $M = (0.028, 0.033, 0.049)$ respectively when calculating M for $r/\sigma \geq 1$.

Increasing $\kappa\sigma$ to 10 makes the potential shorter ranged and steeper. In this case, polydispersity appears to have more of an impact; specifically, $P = 10\%$ undershoots the known

potential. However, as we saw for $\kappa\sigma = 5$, truncating $U(r)$ at $r/\sigma \geq 1$ results in nearly identical extrapolated pair potentials at all levels of polydispersity. For $P=(0,5,10)\%$ we find $M = (0.030, 0.041, 0.080)$ respectively when calculating M for $r/\sigma \geq 1$.

For a system with $\epsilon = 43$ and $\kappa\sigma = 20$, the range of the potential, with respect to the surface of the particle, is roughly equal to the case where $\epsilon = 3$ and $\kappa\sigma = 10$, however it increases more rapidly at small r/σ . This rapid increase in interaction strength results in a system where the diameter of the particle effectively increases (since it is unlikely for particles to interact when $U(r)/k_bT > 10$). Hence, the effective interaction is actually shorter-ranged than $\epsilon = 3$ and $\kappa\sigma = 10$ (i.e. the interaction can be thought of as shorter-ranged and radially shifted outwards from the surface of the particle). This is particularly evident as even the $P = 0\%$ system has trouble resolving the known pair potential well at small r/σ . The effect of polydispersity seems more pronounced than the other systems, undershooting the known potential in both the 5% and 10% cases. In this case, simply truncating our extrapolation at $r/\sigma \geq 1$ is not sufficient to minimize the impact of polydispersity. For $P=(0,5,10)\%$ we have $M = (0.302, 0.47, 0.59)$ respectively when calculating M for $r/\sigma \geq 1$. However, we note that for $r/\sigma \geq 1.125$, we are able to resolve the potential reasonably well for all levels of polydispersity.

From this we can conclude that as the range of the potential decreases, the effect of polydispersity increases. This can be understood as arising from the fact that as the potential acts over shorter distances, the likelihood of close contact increases. In a polydisperse system, where a subset of particles have diameters smaller than the average, we will observe a greater number of particles at small separations of $g(r, \phi)$ within the excluded volume region. Thus, we can expect that relatively short-ranged potentials (or those that are effectively short-ranged) will show a stronger effect of polydispersity and our measurements of ϵ will be less accurate than κ . As a general rule, we should exclude any values of the derived potential that occur for $r/\sigma < 1$ and apply extra scrutiny to any values at small r/σ , especially in systems where the derived potential appears short-ranged. Additionally, any potential estimation method that relies on $g(r, \phi)$ will suffer from this same issues regarding polydispersity and very short-ranged potentials.

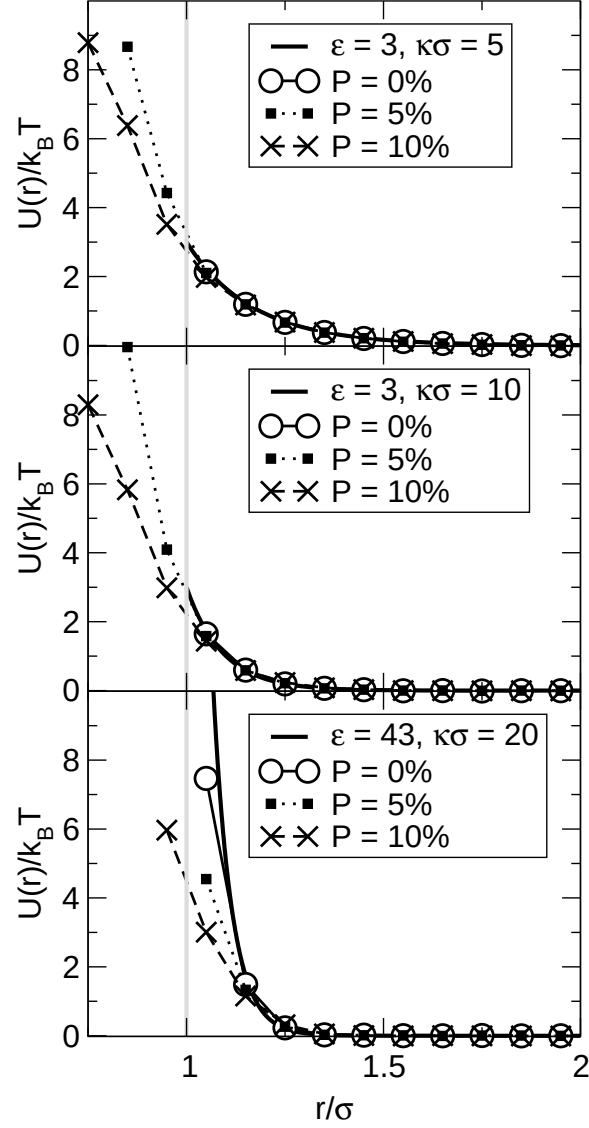


FIG. 7. Comparison of extrapolated potentials with different levels of polydispersity. The grey line denotes the excluded volume region, which corresponds the minimum separation between two average sized particles.

IV. EXPERIMENTAL RESULTS

A. Analysis of Pure DOP System

To test the validity of the potential derivation method in experiment, we first considered PMMA/PHSA particles in pure DOP. We collected data for a range of $\phi = (0.005, 0.007, 0.008, 0.012, 0.018, 0.022, 0.042)$, as summarized in table IV A. For the three lowest values

of $\phi = (0.005, 0.007, 0.008)$, a large number of samples volumes were used for statistical purposes (see appendix regarding error scaling in $g(r)$). Figure 8 plots the average $g(r, \phi)$ for $\phi = (0.005 - 0.022)$ where the bin shell size $\Delta r = 0.1\mu\text{m}$ (10% of the particle diameter) to balance the competing constraints of signal to noise and spatial resolution of the potential. At these charge and solvent conditions, we observed no particles in the inner most shells of $g(r, \phi)$. This result is consistent with repulsive pair interactions, as reported for similar systems^{21,29}. Error bars represent the standard error of the mean of $g(r, \phi)$.

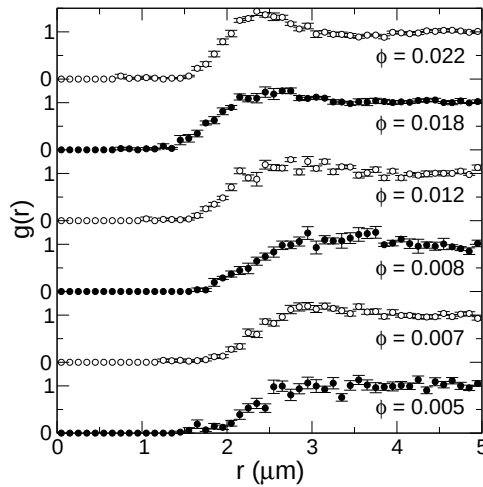


FIG. 8. $g(r, \phi)$ for PMMA/PHSA particle system in pure DOP for $\phi = (0.005, 0.007, 0.008, 0.012, 0.018, 0.022)$ respectively from the bottom.

Figures 9A-C plot $-\ln[g(r, \phi)]$ (i.e. $W(r, \phi)$) as a function of ϕ for $0.005 < \phi < 0.042$ for $r = (1.75, 1.85, 1.95) \mu\text{m}$ for the pure DOP system. As we saw in the simulations (see Figure 2), there is a clear region that displays linear behavior; the crossover between “dilute” and “concentrated” appears at ~ 0.0125 which is nearly identical to the value of $\phi_{max, median} \sim 0.015$ approximated from Figure 3 for $\epsilon = 27$ and $\kappa\sigma = 2.2$ from table II C 1.

The pair potential calculated using the extrapolation method for PMMA/PHSA in the pure DOP solvent is plotted Figure 10. $U(r)/k_B T$ is qualitatively consistent with long-range repulsive interactions, as reported for similar systems²⁹. Error bars plotted are standard error showing the data is precise. The theoretical description of the potential (derived from electrokinetics and the one parameter fit of the unknown solvent conductivity) is also plotted in Figure 10 as reported in table II C 1. These two potentials are in agreement; the

ϕ	N_{total}	Total # of image volumes
0.005	7216	36
0.007	10911	26
0.008	5772	12
0.012	4686	6
0.018	6842	6
0.022	8279	6
0.042	15997	6

TABLE II. Pure DOP solution. N_{total} refers to the total number of particles from the multiple image volumes used in the calculation of $g(r, \phi)$.

average magnitude of the deviation between the extrapolated potential and the theoretical prediction is $M = 0.2$. Note that we expect the value of M to be greater for the experimental system than simulation due to experimental noise; e.g. $M = 0.15$ when comparing the raw data to a best fit of the form of the Yukawa potential. We additionally plot $W(r, 0.022)$ and $W(r, 0.008)$. As we saw in our simulations, $W(r, \phi)$ calculated from even relatively low ϕ values may drastically underestimate the potential (see Figure 10), and the only way to determine this would be to collect additional datasets. In Figure 10 we plot $W(r, 0.022)$ where $M = 0.65$, noting that even this relatively low volume fraction provides a poor estimate of the potential. We also plot $W(r, 0.008)$ which matches both the extrapolated and theory potential well, with $M = 0.18$.

B. Effect of TBAC Addition

To assess the extent to which the method can resolve differences in pair potential interactions that are relevant for self-assembly, we performed experiments in which the range of repulsive interactions are reduced by the addition of electrolyte. We followed the same procedure previously outlined. We collected data at $\phi = (0.012, 0.019, 0.024, 0.037, 0.049)$ for the 10 μ M TBAC system and at $\phi = (0.012, 0.018, 0.031, 0.039, 0.052)$ for the 2mM TBAC system. For both TBAC concentrations, we observed that the onset of finite $g(r, \phi)$

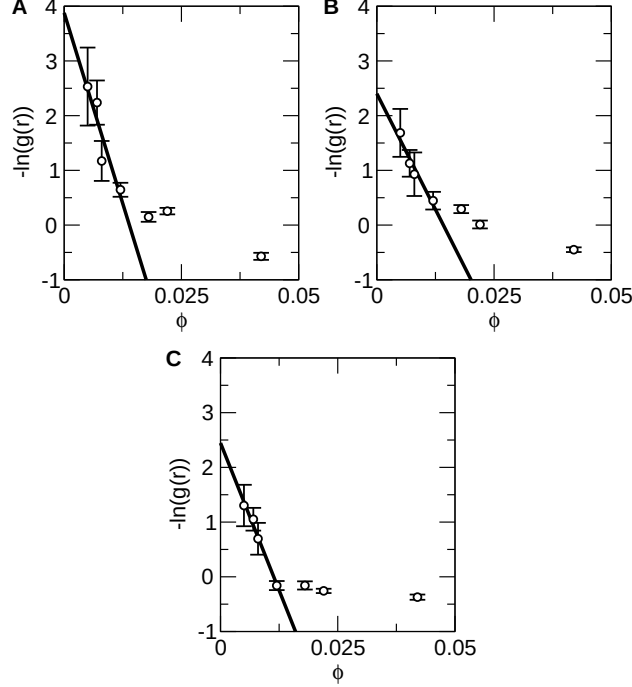


FIG. 9. $W(r, \phi)$ vs. ϕ for radial positions of (A) $r = 1.75 \mu\text{m}$, (B) $r = 1.85 \mu\text{m}$, and (C) $r = 1.95 \mu\text{m}$ for the pure DOP system. The linear, “dilute” regime appears for $\phi < 0.0125$.

is shifted to smaller radial distances (see appendix for more detail). This shift qualitatively indicates that TBAC addition moderates repulsive interactions in the system. This shift also affects the limit of linearity. For example, for the two cases of added salt ($[\text{TBAC}] = 10 \mu\text{M}$ and 2 mM) we found that linearity was maintained out to $\phi \sim 0.05$ which corresponded to the highest volume fraction studied. This increase in the limit of linearity is consistent with the simulations, for which $\phi_{\text{max,median}} \sim 0.1$ from Figure 3. That is, compared to the case of pure DOP, where linearity is found only for $\phi < 0.0125$, these results coincide with an expected shift due to an increase in the screening of the repulsive interactions shown in simulation.

The extrapolated pair potentials for the systems with TBAC are plotted in Figure 11. Visually, we find good agreement between the theoretical potential calculated from electrokinetics for $10\mu\text{M}$ system where $M = 0.35$, as shown in Figure 11A . For $[\text{TBAC}] = 2 \text{ mM}$, we find that the extrapolated potential does not provide as close a match as the pure DOP and $10\mu\text{M}$ systems when compared to electrokinetic-based potential; for $[\text{TBAC}] = 2 \text{ mM}$, $M = 0.84$. The 2mM TBAC system is nearly consistent with simple excluded volume interaction; the transition to the repulsive portion of the potential is abrupt and very close

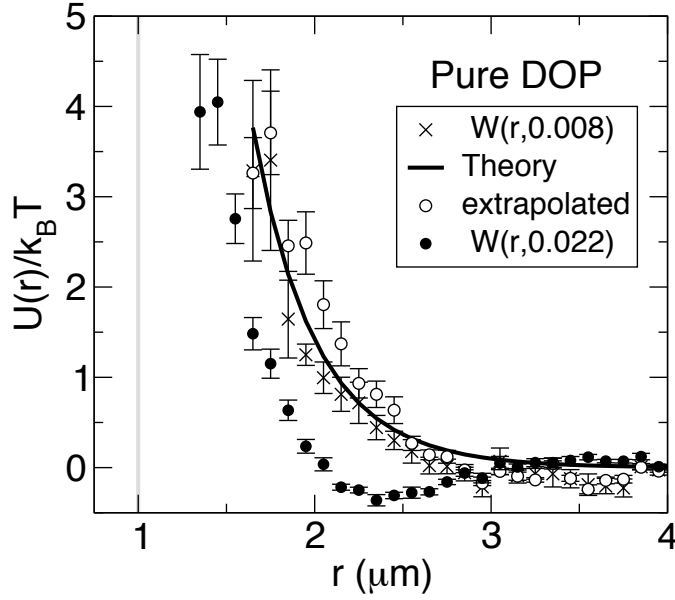


FIG. 10. $U(r)$ for PMMA/PHSA particle system in pure DOP. Screened Coulomb potential calculated from electrokinetics/fitting is shown as a solid line, the extrapolated potential is shown as open circles. $W(r, 0.022)$ is plotted as filled circles, and $W(r, 0.008)$ is plotted with x symbols. The gray line denotes the excluded volume region appearing at $r < 1 \mu\text{m}$.

to the measured diameter of the colloid, with a Debye length of 49 nm. Thus, screened electrostatic interactions extend no further than about 5% of the particle diameter, not too different from the spread in the particle size distribution due to polydispersity which was calculated to be 4%. The effect of polydispersity on this 2mM system is consistent with what was observed in simulation, as discussed previously in Figure 7; as the range of the potential decreases, polydispersity plays a stronger role and the observed ϵ value decreases. However, if we truncate the extrapolated potential at $r \sim 1.25\mu\text{m}$, ignoring any interactions within the excluded volume region and close to the surface of an average particle, we arrive at a more satisfactory description of $U(r)$. We should also note that, as seen in the simulations, we do not resolve $U(r)/k_B T > 10$ for any of the systems studied; however, even given this constraint we can still easily resolve the shape of the potential.

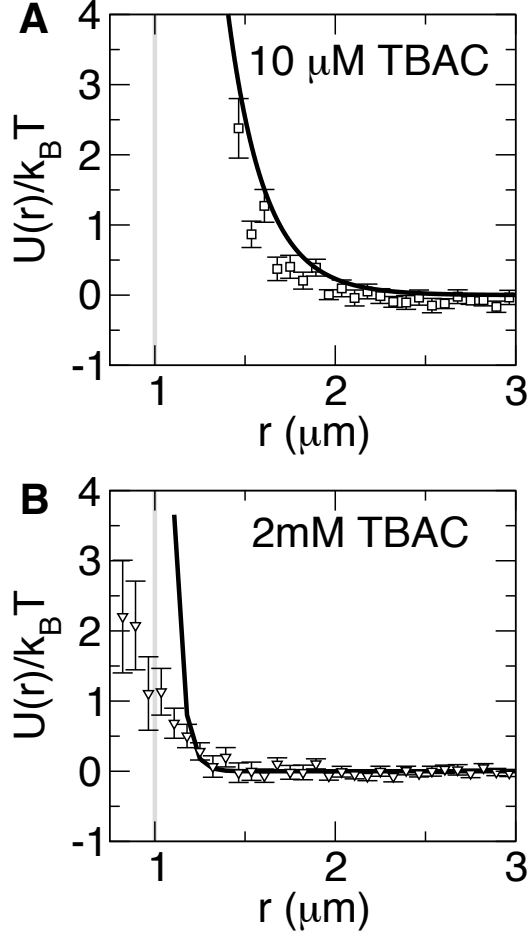


FIG. 11. $U(r)$ for PMMA/PHSA particle system for (A) $10\mu\text{M}$ TBAC, and (B) 2mM TBAC. Screened Coulomb potentials calculated from electrokinetics/fitting are shown as solid lines, extrapolated potentials are shown as symbols. The gray line denotes the excluded volume region appearing at $r < 1\ \mu\text{m}$.

V. CONCLUSIONS

We have presented a method to calculate the pair potential, $U(r)$, between colloidal particles from microscopy. This method relies on extrapolating the potential of mean force, $W(r, \phi)$, to $\phi = 0$. We have shown using MC simulation that this method produces near perfect results for ideal monodisperse colloids. We have used simulation to explore the impact of surface charge and screening length on this method, providing general guidelines for the use of this method over a wide range of parameters. We have also demonstrated that low levels of polydispersity have only a small impact on the accuracy of the calculation

of $U(r)$ for longer-ranged potentials, however the effect is more pronounced as the range of the potential decreases. Further, we have applied this method to experimental colloidal particles using the guidelines established from simulation. We found close agreement of the results of the extrapolation method with theoretical screened Coulombic potentials. As was noted in simulation, the effect of polydispersity becomes stronger for short ranged potentials where the range of the potential is approximately equal to the spread in particle diameter. Moreover, we see that this methodology is well suited to determine the potential for a range of systems, including those that are refractive index matched, particularly for systems where the screening length is on the order of the particle diameter and many body effects are minimal. We anticipate that this methodology can also be used to quantify $U(r)/k_bT$ for attractive systems, assuming the attraction is not so strong as to induce gelation. Additionally, this method can be used in concert with electrokinetic measurements as a means to double-check their validity or used in their place when it is not possible to measure key parameters (e.g. conductivity).

VI. ACKNOWLEDGEMENTS

We thank Lilian Hsiao and Emcee Electronics, Inc. (Venice, Florida) for measurement of the conductivity of the solvent of 10 μ M TBAC in dioctyl phthalate.

REFERENCES

- ¹P. Pusey and W. van Megen, “Observation of a glass-transition in suspensions of spherical colloidal particles,” *Phys. Rev. Lett.*, **59**, 2083 (1987).
- ²E. Sirota, H. Ouyang, S. Sinha, P. Chaikin, J. Axe, and Y. Fujii, “Complete phase-diagram of a charged colloidal system - a synchrotron x-ray-scattering study,” *Phys. Rev. Lett.*, **62**, 1524 (1989).
- ³M. Leunissen, C. Christova, A. Hynninen, C. Royall, A. Campbell, A. Imhof, M. Dijkstra, R. van Roij, and A. van Blaaderen, “Ionic colloidal crystals of oppositely charged particles,” *Nature*, **437**, 235 (2005).
- ⁴S. Ilett, A. Orrock, W. Poon, and P. Pusey, “Phase-behavior of a model colloid-polymer mixture,” *Physical Review E*, **51**, 1344 (1995).

- ⁵M. H. J. Hagen and D. Frenkel, “Determination of phase diagrams for the hard-core attractive yukawa system,” *The Journal of Chemical Physics*, **101**, 4093 (1994).
- ⁶F. E. Azhar, M. Baus, J.-P. Ryckaert, and E. J. Meijer, “Line of triple points for the hard-core yukawa model: A computer simulation study,” *The Journal of Chemical Physics*, **112**, 5121 (2000).
- ⁷I. Hosein and C. Liddell, “Homogeneous, core-shell, and hollow-shell zns colloid-based photonic crystals,” *Langmuir*, **23**, 2892 (2007).
- ⁸T. Ngo, C. Liddell, M. Ghebrebrhan, and J. Joannopoulos, “Tetrastack: Colloidal diamond-inspired structure with omnidirectional photonic band gap for low refractive index contrast,” *Applied Physics Letters*, **88**, 241920 (2006).
- ⁹I. Hosein and C. Liddell, “Convectively assembled nonspherical mushroom cap-based colloidal crystals,” *Langmuir*, **23**, 8810 (2007).
- ¹⁰S. Auer and D. Frenkel, “Prediction of absolute crystal-nucleation rate in hard-sphere colloids,” *Nature*, **409**, 1020 (2001).
- ¹¹H. Butt, B. Cappella, and M. Kappl, “Force measurements with the atomic force microscope: Technique, interpretation and applications,” *Surface Science Reports*, **59**, 1 (2005).
- ¹²J. Israelachvili, *Intermolecular and surface forces* (Academic Press, 1992) pp. xxi, 450 p.
- ¹³M. Bevan and D. Prieve, “Direct measurement of retarded van der waals attraction,” *Langmuir*, **15**, 7925 (1999).
- ¹⁴E. Furst, “Interactions, structure, and microscopic response: Complex fluid rheology using laser tweezers,” *Soft Materials*, **1**, 167 (2003).
- ¹⁵J. C. Crocker and D. G. Grier, “Microscopic measurement of the pair interaction potential of charge-stabilized colloid,” *Physical Review Letters*, **73**, 352 (1994).
- ¹⁶S. K. Sainis, V. Germain, and E. R. Dufresne, “Statistics of particle trajectories at short time intervals reveal fn-scale colloidal forces,” *Physical Review Letters*, **99**, 018303 (2007).
- ¹⁷P. Pusey and W. van Megen, “Phase-behavior of concentrated suspensions of nearly hard colloidal spheres,” *Nature*, **320**, 340 (1986), ISSN 0028-0836.
- ¹⁸P. Habdas and E. Weeks, “Video microscopy of colloidal suspensions and colloidal crystals,” *Current Opinion in Colloid & Interface Science*, **7**, 196 (2002).
- ¹⁹K. Vondermassen, J. Bongers, A. Mueller, and H. Versmold, “Brownian-motion - a tool to determine the pair potential between colloid particles,” *Langmuir*, **10**, 1351 (1994).

- ²⁰C. Royall, D. Aarts, and H. Tanaka, “Fluid structure in colloid-polymer mixtures: the competition between electrostatics and depletion,” *Journal of Physics-Condensed Matter*, **17**, S3401 (2005).
- ²¹C. Royall, A. Louis, and H. Tanaka, “Measuring colloidal interactions with confocal microscopy,” *Journal of Chemical Physics*, **127**, 044507 (2007).
- ²²M. Hsu, E. Dufresne, and D. Weitz, “Charge stabilization in nonpolar solvents,” *Langmuir*, **21**, 4881 (2005).
- ²³H. Wu and M. Bevan, “Direct measurement of single and ensemble average particle-surface potential energy profiles,” *Langmuir*, **21**, 1244 (2005).
- ²⁴P. Lu, E. Zaccarelli, F. Ciulla, A. Schofield, F. Sciortino, and D. Weitz, “Gelation of particles with short-range attraction,” *Nature*, **453**, 499 (2008).
- ²⁵D. Chandler, *Introduction to Modern Statistical Mechanics* (Oxford University Press, 1987) p. 274.
- ²⁶J. W. Merrill, S. K. Sainis, and E. R. Dufresne, “Many-body electrostatic forces between colloidal particles at vanishing ionic strength,” *Physical Review Letters*, **103**, 138301 (2009).
- ²⁷C. P. Royall, M. E. Leunissen, A.-P. Hynninen, M. Dijkstra, and A. van Blaaderen, “Re-entrant melting and freezing in a model system of charged colloids,” *The Journal of Chemical Physics*, **124**, 244706 (2006).
- ²⁸D. Frenkel and B. Smit, *Understanding Molecular Simulation* (Academic Press, Inc. Orlando, FL, USA, 2001).
- ²⁹C. Royall, M. Leunissen, and A. van Blaaderen, “A new colloidal model system to study long-range interactions quantitatively in real space,” *Journal of Physics-Condensed Matter*, **15**, S3581 (2003).
- ³⁰T. Solomon and M. Solomon, “Stacking fault structure in shear-induced colloidal crystallization,” *Journal of Chemical Physics*, **124**, 134905 (2006).
- ³¹L. T. Shereda, R. G. Larson, and M. J. Solomon, “Local stress control of spatiotemporal ordering of colloidal crystals in complex flows,” *Phys. Rev. Lett.*, **101**, 038301 (2008).
- ³²L. Antl, J. Goodwin, R. Hill, R. Ottewill, S. Owens, S. Papworth, and J. Waters, “The preparation of poly(methyl methacrylate) lattices in nonaqueous media,” *Colloids and Surfaces*, **17**, 67 (1986).

- ³³A. Campbell and P. Bartlett, “Fluorescent hard-sphere polymer colloids for confocal microscopy,” *Journal of Colloid and Interface Science*, **256**, 325 (2002).
- ³⁴C. Pathmamanoharan, K. Groot, and J. Dhont, “Preparation and characterization of crosslinked pmma latex particles stabilized by grafted copolymer,” *Colloid and Polymer Science*, **275**, 897 (1997).
- ³⁵W. Russel, D. Saville, and W. Schowalter, *Colloidal dispersions* (1989) pp. xvii, 525 p.
- ³⁶R. Fuoss, “Dependence of the walden product on dielectric constant,” *Proceedings of the National Academy of Sciences of the United States of America*, **45**, 807 (1959).
- ³⁷P. Walden, *Z. Phys. Chem.*, **55**, 207 (1906).
- ³⁸P. Walden, *Z. Phys. Chem.*, **55**, 246 (1906).
- ³⁹J. A. Dean, ed., *Lange’s Handbook of Chemistry (15th Edition)* (McGraw-Hill, 1999) ISBN 978-0-07-016384-3.
- ⁴⁰F. Bautista, L. Rejon, and O. Manero, “The dielectric spectrum and the electrorheological effect in suspensions of varying conductivity - part 2. modeling of the electrorheological effect,” *Colloids and Surfaces a-Physicochemical and Engineering Aspects*, **303**, 191 (2007).
- ⁴¹R. Obrien and L. White, “Electrophoretic mobility of a spherical colloidal particle,” *Journal of the Chemical Society-Faraday Transactions II*, **74**, 1607 (1978).
- ⁴²*CRC Handbook of Chemistry and Physics*, 90th ed. (CRC Press, 2009).
- ⁴³M. Kogan, C. Dibble, R. Rogers, and M. Solomon, “Viscous solvent colloidal system for direct visualization of suspension structure, dynamics and rheology,” *Journal of Colloid and Interface Science*, **318**, 252 (2008).
- ⁴⁴J. Crocker and D. Grier, “Methods of digital video microscopy for colloidal studies,” *Journal of Colloid and Interface Science*, **179**, 298 (1996).
- ⁴⁵P. Varadan and M. Solomon, “Direct visualization of long-range heterogeneous structure in dense colloidal gels,” *Langmuir*, **19**, 509 (2003).
- ⁴⁶C. Dibble, M. Kogan, and M. Solomon, “Structure and dynamics of colloidal depletion gels: Coincidence of transitions and heterogeneity,” *Physical Review E*, **74**, 041403 (2006).
- ⁴⁷J. Crocker and D. Grier, “When like charges attract: The effects of geometrical confinement on long-range colloidal interactions,” *Phys. Rev. Lett.*, **77**, 1897 (1996).
- ⁴⁸A. Ramirez-Saito, C. Bechinger, and J. Arauz-Lara, “Optical microscopy measurement of pair correlation functions,” *Physical Review E*, **74**, 030401 (2006).

⁴⁹J. Baumgartl, J. L. Arauz-Lara, and C. Bechinger, “Like-charge attraction in confinement: myth or truth?” *Soft Matter*, **2**, 631 (2006), ISSN 1744-683X.

⁵⁰R. P. Sear, “Phase separation and crystallisation of polydisperse hard spheres,” *EPL (Europhysics Letters)*, **44**, 531 (1998).

VII. APPENDIX

A. Addition of TBAC to the DOP solvent

In section IV B we explored the addition of TBAC to the DOP solvent. The total number of image volumes/particles collected are summarized in table VII A for the 10 μM solution and VII A for the 2mM solution. The $g(r, \phi)$ data used to calculate the extrapolated $U(r)/k_bT$ (extrapolations were previously shown in Figure 10) are plotted for in Figure 12.

ϕ	N_{total}	Total # of image volumes
0.012	6646	10
0.019	8331	8
0.024	10434	8
0.037	12183	8
0.049	16116	6

TABLE III. [TBAC] = 10 μM .

B. Error scaling in the radial distribution function

Essential to accurately determining the pair potential is generating $g(r, \phi)$ with sufficient accuracy. $g(r, \phi)$ is a measure of the probability of finding a particle at a distance r away from a given reference particle. This distribution function is determined by calculating the distance between all particles pairs and binning them into a histogram; the histogram is then normalized with respect to an ideal gas, where particle histograms are completely

ϕ	N_{total}	Total # of image volumes
0.012	10568	14
0.019	13508	12
0.031	10196	6
0.037	12453	6
0.049	15129	6

TABLE IV. [TBAC] = 2 mM.

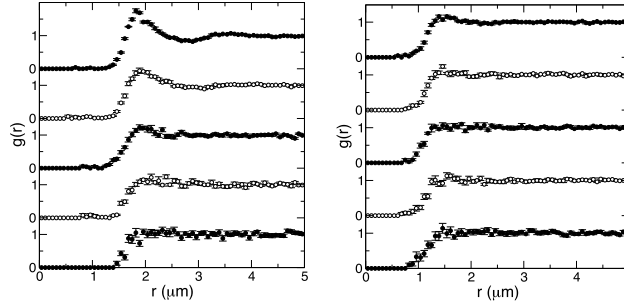


FIG. 12. $g(r, \phi)$ plots for [TBAC] = 10 μ M (left) and [TBAC] = 2 mM (right). Data corresponds to $\phi = (0.012, 0.019, 0.024, 0.037, 0.049)$ [TBAC] = 10 μ M (left) and $\phi = (0.012, 0.019, 0.031, 0.037, 0.049)$ for [TBAC] = 2 mM (right) respectively from the bottom.

uncorrelated. Due to its construction, $g(r, \phi)$ is a spherically averaged measure; therefore, we average over more particle pairs as we consider larger particle separations. In other words, our statistics increase as r increases. This may be problematic since the pair potential we wish to determine acts the strongest at smaller separations where we have the least statistics. Additionally, since we must compute $g(r, \phi)$ at low values of ϕ , it is unlikely to have many particles interacting at small values of r if particles are well distributed in the system (i.e. particles do not aggregate); unlike in a dense system, a single configuration snapshot will not be sufficient to accurately generate $g(r, \phi)$. As such, to determine $U(r)$ accurately, we must establish when we have appropriately gathered sufficient statistics to be confident in $g(r, \phi)$.

We considered the error in $g(r, \phi)$ at a given separation of r to be proportional to $1/\sqrt{N_{bin}}$, where N_{bin} is the number of particles in the bin. By this construction, our maximum error

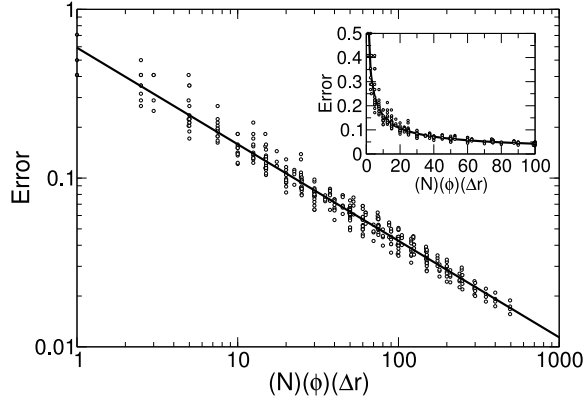


FIG. 13. Error scaling in $g(r, \phi)$ for a combination of Yukawa systems with $\epsilon = 3$ and $\kappa = (3.0, 1.5, 0.5, 0.25)$, over a range of volume fractions, $\phi = (0.001, 0.005, 0.01, 0.02)$, and $\Delta r = (0.05, 0.15, 0.25)$.

is $1/\sqrt{2} = 0.707$ and our minimum error will approach 0. There are three main factors that impact this value: the error decreases as we increase the total number of particles considered, N_{total} (i.e. the sum of all particles in all the samples used to construct $g(r, \phi)$); the error decreases as we increase our volume fraction, ϕ ; and the error decreases as we increase the width of the bin, Δr . In Figure 13 we plot $1/\sqrt{N_{bin}}$ vs. $(N_{total})(\phi)(\Delta r)$ for a combination of Yukawa systems; here we have chosen to plot the data for a bin close to the surface of the particle, specifically $r/\sigma = 1.125$, as this should be characteristic of the maximum error in the system. We simulated four different potentials; we fixed $\epsilon = 3$ and varied the inverse screening length, specifically $\kappa = (3.0, 1.5, 0.5, 0.25)$. For each potential we performed simulations over a range of volume fractions, $\phi = (0.001, 0.005, 0.01, 0.02)$ and then analyzed each of these simulations using three bin sizes, $\Delta r = (0.05, 0.15, 0.25)$. We plotted the data from these four potentials in Figure 13 finding that the error roughly scales as a power law with exponent -0.57. The inset of Figure 13 plots the data on a standard axis; it is clear from this plot that our error is most rapidly decreasing in the range of $1 < (N_{total})(\phi)(\Delta r) < 10$. At values of $(N_{total})(\phi)(\Delta r) > 10$, our error decreases very slowly. Thus for the best statistics in the $g(r, \phi)$, a rough guideline should be to perform enough samples such that $(N_{total})(\phi)(\Delta r) > 10$. For our simulations $\Delta r = 0.1$ and $(N_{total} = 1000000)$, thus, even for our lowest volume fraction of $\phi = 0.001$, this condition is met.

Similarly, Figure 14 summarizes the relationship between the precision of the measured $g(r, \phi)$ and properties of the experiments, including the number of particles, the volume fraction of the specimen, and the bin size of each point in $g(r, \phi)$. We see that the error in $g(r, \phi)$ is a weak function of the combination $(N_{total})(\phi)(\Delta r)$, scaling as power law with exponent -0.79. Figure 14 can be applied to determine experimental conditions for pair potential characterization. For example, for a relative error of $\sim 10\%$ in the radial distribution, Figure 14 requires $(N_{total})(\phi)(\Delta r) \sim 7$. For a volume fraction 0.01 with $1 \mu\text{m}$ particles in which $\Delta r = 0.1 \mu\text{m}$, this relative error would require on the order of 7000 particles.

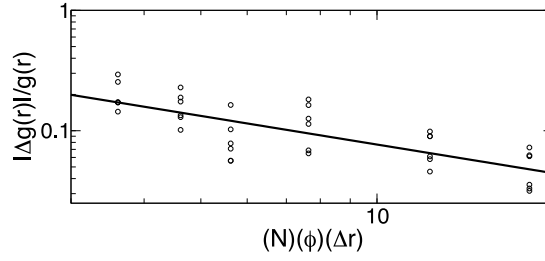


FIG. 14. Error scaling in $g(r, \phi)$ as a function of number of particles, volume fraction, and bin size for pure DOP, no salt case. Data taken from four different radial positions, $r = (2.05, 2.15, 2.35, 2.55, 2.75, 3.05) \mu\text{m}$. Line drawn is power law fit with exponent -0.79.